

Pauli susceptibility of A_3C_{60} ($A=K, Rb$)

F. Aryasetiawan^(1,2), O. Gunnarsson⁽¹⁾, E. Koch⁽³⁾ and R.M. Martin⁽³⁾

⁽¹⁾ *Max-Planck-Institut für Festkörperforschung, D-70506 Stuttgart, Germany*

⁽²⁾ *Department of Theoretical Physics, University of Lund, Sölvegatan 14 A, S-223 62 Lund, Sweden*

⁽³⁾ *Department of Physics, University of Illinois, Urbana, Illinois 61801*

(February 1, 2008)

The Pauli paramagnetic susceptibility of A_3C_{60} ($A=K, Rb$) compounds is calculated. A lattice quantum Monte Carlo method is applied to a multi-band Hubbard model, including the on-site Coulomb interaction U . It is found that the many-body enhancement of the susceptibility is of the order of a factor of three. This reconciles estimates of the density of states from the susceptibility with other estimates. The enhancement is an example of a substantial many-body effect in the doped fullerenes.

The Pauli paramagnetic susceptibility χ is interesting for several reasons. Firstly, χ is enhanced by many-body effects relative to its value χ_0 for noninteracting electrons, and χ/χ_0 is one measure of the strength of the many-body effects in the system. In the alkali-doped C_{60} compounds, A_3C_{60} ($A=K, Rb$) the Coulomb interaction U between two electrons on the same molecule is large¹ compared with the width W of the partly filled t_{1u} band, with typical estimates $U/W \sim 1.5 - 2.5$.² In view of this large ratio, one expects very strong many-body effects for these systems. Up to now, however, there seems to be no unambiguous signature of such strong effects.

Secondly, χ_0 is related to the density of states $N(0)$ at the Fermi energy, and values of $N(0)$ can be extracted from χ if the enhancement χ/χ_0 is known. $N(0)$ is important for the superconductivity and the electron-phonon interaction λ , since theoretical calculations give $\lambda/N(0)$, while some experimental (e.g., neutron³ and Raman scattering⁴) estimates give $\lambda N(0)$ and others (e.g., photoemission from C_{60} molecules⁵) give $\lambda/N(0)$. The estimate of $N(0)$ is therefore crucial for obtaining values of λ and for our understanding of the superconductivity. Typically, for K_3C_{60} band structure calculations give $N(0) \sim 6 - 9$ states/(eV-spin).⁶⁻¹¹ Estimates based on the specific heat and the NMR relaxation rate give $N(0) \sim 5 - 6$ states/(eV-spin)¹² and $N(0) \sim 7.2$ states/(eV-spin),¹³ respectively. On the other hand, much larger values $N(0) \sim 10 - 16$ states/(eV-spin) for K_3C_{60} are deduced from the susceptibility,¹⁴⁻¹⁷ if many-body effects are neglected. A substantial many-body enhancement (factor 2-3) for the susceptibility,¹⁴ could essentially reconcile these rather different estimates. On the other hand, density functional calculations in the local density approximation (LDA) find that the enhancement is only about a factor of 1.3-1.4.¹³ We note that $N(0)$ here refers to densities of states defined in somewhat different ways depending on the experiment, as discussed below.

We have used a lattice quantum Monte Carlo method^{18,2} for calculating the Pauli susceptibility for a

multi-band Hubbard model of the system. For a small system with four C_{60} molecules, we demonstrate that this method gives an accurate enhancement of the susceptibility. For realistic values of the parameters, the susceptibility is enhanced by about a factor of three, which essentially reconciles estimates of $N(0)$ based on the susceptibility with other estimates.

In the presence of a small external magnetic field $\mathcal{H}$, the energy of the system can be written as

$$E(\mathcal{M}) = E_0(\mathcal{M}) - \mathcal{M}\mathcal{H} \approx E_0 + \frac{1}{2}\alpha\mathcal{M}^2 - \mathcal{M}\mathcal{H}, \quad (1)$$

where $\mathcal{M} \equiv -\mu_B(N_\uparrow - N_\downarrow)$ is the magnetic moment of the system, with μ_B being the Bohr magneton and N_σ the number of electrons with spin σ . $E_0(\mathcal{M})$ is the energy of the system with a moment $\mathcal{M}$ in the absence of an external field. Minimizing the energy with respect to $\mathcal{M}$, we obtain the susceptibility

$$\chi \equiv \frac{\mathcal{M}}{\mathcal{H}} = \frac{1}{\alpha}. \quad (2)$$

In the following we therefore calculate $E_0(\mathcal{M})$ for the interacting and noninteracting ($U = 0$) systems, from which we obtain the many-body enhancement χ/χ_0 .

We use a multi-band Hubbard model of the A_3C_{60} compounds

$$H = \sum_{i\sigma} \sum_{m=1}^3 \varepsilon_{t_{1u}} n_{i\sigma m} + \sum_{\langle ij \rangle \sigma m m'} t_{ijmm'} \psi_{i\sigma m}^\dagger \psi_{j\sigma m'} + U \sum_i \sum_{\sigma m < \sigma' m'} n_{i\sigma m} n_{i\sigma' m'}, \quad (3)$$

where the first term describes the three-fold degenerate t_{1u} states on the sites i and with orbital (m) and spin (σ) indices. The second term describes the hopping between the sites, and the third term describes the Coulomb on-site interaction. Multiplet effects and the electron-phonon interaction have been neglected. In A_3C_{60} , the C_{60} molecules are preferentially in one of two possible orientations in an essentially random way.¹⁹ We

take this into account by having a large cell, where each molecule takes one of the two preferred orientations in a random way, and the hopping matrix elements between two molecules take into account the orientations of these two molecules.^{20,21}

To calculate the energy of the model in Eq. (3), we use a $T = 0$ projection lattice Monte Carlo method, introduced by ten Haaf *et al.*¹⁸ In this method a trial function is constructed from a Slater determinant, using a Gutzwiller Ansatz.²² An approximate ground-state is then projected out in a diffusion Monte Carlo (DMC) approach, using a “fixed node” approximation. This method has been used to study the condition for a Mott-Hubbard transition in A_3C_{60} .²

To test the accuracy of the DMC approach, we have first applied the method to a cluster of four C_{60} molecules. This cluster is so small that we can also obtain the exact solution for the model in Eq. (3), using exact diagonalization. We then calculate the coefficient α in Eq. (1) by considering the energy for $N_\uparrow - N_\downarrow = 0$ and 2. The DMC and exact results are compared in Table I. We can see that the DMC method is quite accurate in this case, and if a similar accuracy is obtained for larger systems, it is quite sufficient.

TABLE I. The enhancement of the susceptibility for a model with four C_{60} molecules according to diffusion Monte Carlo (DMC) and exact calculations as a function of the Coulomb energy U . The band width is $W = 0.58$ eV.

U	χ/χ_0	
	DMC	Exact
1.0	1.89	1.93
1.25	2.20	2.26
1.50	2.63	2.69

The enhancement of the susceptibility is sensitive to the density of states (DOS) close to the Fermi energy E_F . For small and intermediate size clusters of C_{60} molecules, the DOS depends on the orientations of the molecules, while for large clusters the DOS rapidly converges. Since we can only treat intermediate size clusters ($\sim (32 - 64)$ molecules) in DMC, we have therefore chosen orientations which in a one-particle approximation give similar DOS close to E_F as for very large clusters.

In Fig. 1 we show results for the total energy as a function of $\mathcal{M} \sim N_\uparrow - N_\downarrow$ for different values of U . The results can be rather well fitted by parabolas, although the precise parameters of the parabolas have a certain dependence on the range of $\mathcal{M}$ considered. From these slopes we can immediately deduce values of the enhancement χ/χ_0 . In Fig. 2 the inverse of the enhancement χ_0/χ is shown. It is immediately clear that the enhancement grows with U and that χ would diverge for U a bit larger than 2 eV, if no other transition (e.g., antiferromagnetic) happened before. Estimates of U are typically in the range 1-1.5 eV, giving an enhancement of the susceptibility by about a factor of three. Qualitatively

similar results have been obtained for a Hubbard model without orbital degeneracy and in the limit of infinite dimensions.²⁶

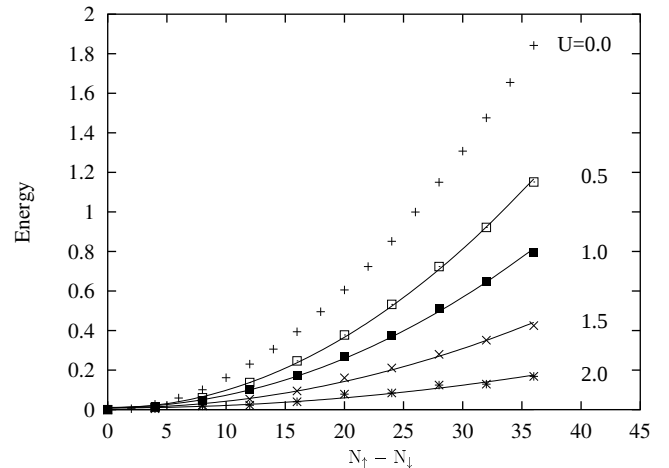


FIG. 1. The energy as a function of $N_\uparrow - N_\downarrow \sim \mathcal{M}$ relative to the energy for $\mathcal{M}=0$. Second order curves have been fitted to the energies. Results for $U = 0, 0.5, 1.0, 1.5$ and 2.0 eV are shown. The calculations are for 32 molecules and the energy is in eV.

Within the Hartree-Fock approximation, the susceptibility behaves as

$$\frac{\chi_0}{\chi} \sim 1 - \frac{N(0)}{3}U, \quad (4)$$

where the factor three comes from the three-fold degeneracy and $N(0)$ is the density of states per spin, which here is about 5.5 states/(eV-spin). Here we have assumed that the three orbitals are equivalent. The DMC results show a similar behavior, but with a prefactor in front of U , which is between a factor of four and five times smaller. This large change in the prefactor illustrates the importance of correlation in these systems.

To deduce $N(0)$ we need to know the Pauli (paramagnetic) susceptibility. Measurements using a SQUID may also contain a diamagnetic contribution, while EPR measurements do not. In Table II we show various experimental results converted to $N(0)$. From the SQUID results, diamagnetic contributions estimated by the respective authors have been subtracted, but the many-body enhancement has *not* been considered. We can see that the results range between 10 and 16 states/(eV-spin). If we consider a many-body enhancement of a factor of three, as deduced above, these results would be reduced to about $N^{sus}(0) \sim 4 - 5$ states/(eV-spin).

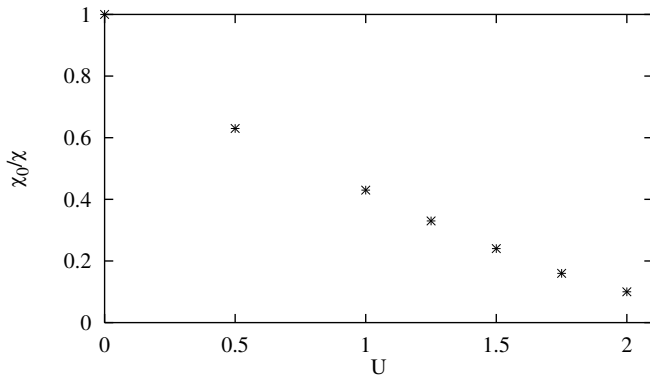


FIG. 2. The inverse enhancement χ_0/χ of the susceptibility for a cluster with 32 molecules as a function of the Coulomb interaction U (in eV). The band width is 0.66 eV.

Up to now we have not fully considered differences in the definition of the density of states $N(0)$ deduced from different sources. Calculations of the electron-phonon interaction λ are usually based on band structure calculations, giving a density of states $N_0(0)$ for noninteracting electrons. The electron-electron interaction modifies $N_0(0)$ to its interacting value $\mathcal{N}(0)$ (density of quasi-particle states), which should be used in the calculation of λ .²³ This density of states enters in the specific heat²⁴

$$\frac{C_v}{T} \sim \mathcal{N}(0)(1 + \lambda), \quad (5)$$

where the last factor is due to the electron-phonon interaction, assuming that the band width is large compared with the phonon frequency.²⁵ In the same approximation, the susceptibility can be written as²⁴

$$\chi \sim \frac{\mathcal{N}(0)}{1 + F_0^a}, \quad (6)$$

where F_0^a is a Landau parameter and $1/(1 + F_0^a)$ can be considered as a Stoner enhancement. Our calculation χ/χ_0 includes both the factors $\mathcal{N}(0)/N_0(0)$ and $(1 + F_0^a)$. Within the present Monte Carlo technique it is not possible to calculate the specific heat, and we can therefore not separate the two contributions. The value of $N^{susc}(0)$ deduced from the susceptibility, after dividing out many-body effects, should therefore primarily be compared with the results obtained from band structure calculations. The band structure calculations have been performed for orientationally ordered systems and give $N_0^{ord} \sim 6 - 9$ states/(eV-spin). Since the real systems have orientational disorder, we estimate the corresponding density of states by solving the Hamiltonian (3) for $U = 0$ and orientational disorder. Comparison with calculations for ordered systems suggests a reduction of $N(0)$ by about 15 – 20% to $N_0^{disord}(0) \sim 5 - 7$ states/(eV-spin). This is in rather good agreement with $N^{susc}(0) \sim 4 - 5$ states/(eV-spin).

It is interesting that the estimate of $\mathcal{N}(0) \sim 5 - 6$ states/(eV-spin) based on the specific heat¹² is comparable to

the noninteracting result $N_0^{disord}(0) \sim 5 - 7$ states/(eV-spin). In contrast to what has been found for the non-degenerate Hubbard model in infinite dimensions,²⁶ this surprising observation suggests that the enhancement of the density of states is small in the A_3C_{60} compounds or that there may even be a reduction. If this is indeed the case, then the enhancement of the susceptibility would be a Stoner enhancement, and the $N_0^{susc}(0)$ obtained from the susceptibility, after dividing out the many-body enhancement, could be compared with other experimental estimates of $N(0)$. We then find that these experimental estimates are essentially brought in line with each other and with the band structure estimates, giving $N(0) \sim 5 - 7$ states/(eV-spin) for K_3C_{60} .

In our model and in the calculations of the susceptibility, we have neglected multiplet effects and the electron-phonon interaction, which are now discussed. The electron-phonon interaction leads to an increase of the density of states at the Fermi energy, due to the reduced dispersion of states within roughly a phonon energy of the Fermi energy. This does not influence the susceptibility, if the phonon energies are small compared with the electronic energies.²⁷ Although this assumption may not be entirely satisfied for A_3C_{60} and interesting effects may result from the finite band width,²⁸ we here neglect the effects of the electron-phonon interaction on the density of states. Instead we focus on how the electron-phonon interaction influences the moment formation on the C_{60} molecules.

TABLE II. The density of states $N(0)$ (per eV and spin) for K_3C_{60} as deduced from susceptibility measurements. The results have *not* been corrected for the Stoner enhancement, which would lead to reduced estimates of $N(0)$.

$N(0)$ (K_3C_{60})	Method	Reference
14	SQUID	Ramirez <i>et al.</i> ¹⁴
16	SQUID	Wong <i>et al.</i> ¹⁵
11	EPR	Wong <i>et al.</i> ¹⁵
15	EPR	Tanigaki <i>et al.</i> ¹⁶
10	EPR	Wang <i>et al.</i> ¹⁷

If the multiplets are neglected but the electron-phonon interaction (Jahn-Teller effect) is considered, the lowest spin 1/2 state is favored over the spin 3/2 state, according to calculations for the lowest state of each multiplicity for a free molecule.²⁹ The energy lowering of the spin 1/2 relative to the spin 3/2 state may be as large as 0.3 eV.³⁰ This suppresses the formation of moments and probably tends to reduce the susceptibility. On the other hand, the multiplet effects should favor the formation of moments on the C_{60} molecules, by giving preference to states with the spin 3/2.

The multiplet effects lead to five spin 1/2 states with the energy $3K$ and three spin 1/2 states with the energy $5K$ relative to the spin 3/2 state. Here K is the exchange integral between two t_{1u} orbitals, and we have assumed that the Coulomb integral (U_{xx}) between equal

orbitals is $2K$ larger than the one (U_{xy}) between different orbitals. To estimate K , we have used a simple model, where the Coulomb integral between two $2p$ -charge distributions on two carbon atoms goes as e^2/R , where R is the separation between the two atoms.³¹ The on-site interaction was assumed to be 15 eV. Without screening we find that $K = 0.12$ eV. This probably overestimates the multiplet effects. An alternative estimate is obtained by using RPA screening of the Coulomb interaction. We then find $K = 0.030$ eV. A similar result (0.024 eV) was also found by Joubert, using a density functional approach.³²

From the numbers above it follows that there should be a partial cancellation between electron-phonon and multiplet effects. Depending on which numbers are used, either effect could be argued to be larger. If the electron-phonon effects win, this may lead to a somewhat smaller enhancement of the susceptibility than was found above (Fig. 2).

We have calculated the Pauli susceptibility of the doped fullerenes A_3C_{60} ($A = K, Rb$). The enhancement is of the order of a factor of three, which allows us to reconcile the estimates of the density of states from the susceptibility with other estimates. This suggests that for K_3C_{60} $N(0) \sim 5 - 7$ states/(eV-spin). This value is only slightly smaller than a value ($N(0) = 7.2$) used recently to provide support for an electron-phonon mechanism driving the superconductivity in K_3C_{60} ,⁵ but substantially smaller than some values used in early theoretical discussions. The susceptibility enhancement is appreciably larger than the one (factor 1.3-1.4) found in the LDA, and it is one of the first explicit examples of important many-body effects, expected to be found in these systems. Comparison with Hartree-Fock calculations shows, however, that the enhancement is about four to five times smaller than the HF result, illustrating the importance of correlation effects.

¹ R.W. Lof, M.A. van Veenendaal, B. Koopmans, H.T. Jonkman, and G.A. Sawatzky, 1992, Phys. Rev. Lett. **68**, 3924.

² O. Gunnarsson, E. Koch, and R.M. Martin, Phys. Rev. B **54**, R11026 (1996).

³ K. Prassides, C. Christides, M.J. Rosseinsky, J. Tomkinson, D.W. Murphy, and R.C. Haddon, Europhys. Lett. **19**, 629 (1992).

⁴ Winter, J. and H. Kuzmany, 1996, Phys. Rev. B **53**, 655.

⁵ O. Gunnarsson, H. Handschuh, P.S. Bechthold, B. Kessler, G. Ganteför, and W. Eberhardt, Phys. Rev. Lett. **74**, 1875 (1995).

⁶ S.C. Erwin and W.E. Pickett, Science **254**, 842 (1991).

- ⁷ N. Troullier and J.L. Martins, Phys. Rev. B **46**, 1766 (1992).
- ⁸ M.Z. Huang, Y.-N. Xu and W.Y. Ching, Phys. Rev. B **46**, 6572 (1992).
- ⁹ S. Satpathy, V.P. Antropov, O.K. Andersen, O. Jepsen, O. Gunnarsson, and A.I. Liechtenstein, Phys. Rev. B **46**, 1773 (1992).
- ¹⁰ D.L. Novikov, V.A. Gubanov and A.J. Freeman, Physica C **191**, 399 (1992).
- ¹¹ V.P. Antropov *et al.* (unpublished).
- ¹² G.J. Burkhardt, and C. Meingast, Phys. Rev. B **54**, R6865 (1996).
- ¹³ V.P. Antropov, I.I. Mazin, O.K. Andersen, A.I. Liechtenstein, and O. Jepsen, Phys. Rev. B **47**, 12 373 (1993).
- ¹⁴ A.P. Ramirez, M.J. Rosseinsky, D.W. Murphy, and R.C. Haddon, Phys. Rev. Lett. **69**, 1687 (1992).
- ¹⁵ W.H. Wong, M.E. Hanson, W.G. Clark, G. Grüner, J.D. Thompson, R.L. Whetten, S.-M. Huang, R.B. Kaner, F. Diederich, P. Petit, J.-J. Andre and K. Holczer, Europhys. Lett. **18**, 79 (1992).
- ¹⁶ K. Tanigaki, M. Kosaka, T. Manako, Y. Kubo, I. Hirose, K. Uchida, and K. Prassides, Chem. Phys. Lett. **240**, 627 (1995).
- ¹⁷ D. Wang, Solid State Commun. **94**, 767 (1995).
- ¹⁸ F.B. ten Haaf, H.J.M. van Bommel, J.M.J. van Leeuwen, W. van Saarloos, and D.M. Ceperley, Phys. Rev. B **51**, 353 (1995); H.J.M. van Bommel, D.F.B. van Haaf, W. van Saarloos, J.M.J. van Leeuwen, and G. An, Phys. Rev. Lett. **72**, 2442 (1994).
- ¹⁹ P.W. Stephens, L. Mihaly, P.L. Lee, R.L. Whetten, S.-M. Huang, R. Kaner, F. Diederich, and K. Holczer, 1991, Nature **351**, 632.
- ²⁰ O. Gunnarsson, S. Satpathy, O. Jepsen, and O.K. Andersen, Phys. Rev. Lett. **67**, 3002 (1991).
- ²¹ I.I. Mazin, A.I. Liechtenstein, O. Gunnarsson, O.K. Andersen, V.P. Antropov, and S.E. Burkov, Phys. Rev. Lett. **26**, 4142 (1993).
- ²² M.C. Gutzwiller *et al.*, Phys. Rev. **137**, A1726 (1965).
- ²³ D.J. Scalapino, in *Superconductivity*, edited by R.D. Parks, Dekker (New York, 1969), p. 449.
- ²⁴ D. Pines and P. Noziere, *The theory of quantum liquids*, Benjamin (New York, 1966).
- ²⁵ G. Grimvall, *The electron-phonon interaction in metals*, North-Holland, (1981), p. 212.
- ²⁶ A. Georges, G. Kotliar, W. Krauth, and M.J. Rozenberg, Rev. Mod. Phys. **68**, 13 (1996).
- ²⁷ R.E. Prange and A. Sachs, Phys. Rev. **158**, 672 (1967).
- ²⁸ A.I. Liechtenstein, O. Gunnarsson, M. Knupfer, J. Fink, and J.F. Armbruster, J. Phys.: Cond. Matter **8**, 4001 (1996).
- ²⁹ A. Auerbach, N. Manini and E. Tosatti, Phys. Rev. B **49**, 12998 (1994). N. Manini, E. Tosatti and A. Auerbach, Phys. Rev. **49**, 13008 (1994).
- ³⁰ O. Gunnarsson, Phys. Rev. B **51**, 3493 (1995).
- ³¹ Gunnarsson, O., D. Rainer, and G. Zwicknagl, 1992, Int. J. Mod. Phys. B **6**, 3993.
- ³² D.P. Joubert, J. Phys.: Condens. Matter **5**, 8047 (1993).